



40CrMnMoS8-6 Tool Steel

Quality 40CrMnMoS8-6 tool steel cut and delivered straight to your tool room.

40CrMnMoS8-6 tool steel suppliers and stockholders delivering to the whole of the UK.


West Yorkshire Steel are stockholders and suppliers of 40CrMnMoS8-6 steel round bar, flat bar and plate. 40CrMnMoS8-6 is a high tensile alloy tool steel grade supplied in the hardened and tempered condition. With its higher sulphur content it offer better machinability than [40CrMnMo7](#) plastic mould tool steel grade.

Form of Supply

West Yorkshire Steel are stockists and suppliers of plate, round bar and flat bar. Rectangular pieces in grade 40CrMnMoS8-6 can be sawn from flat bar or block to your specific sizes. Diameters can be sawn to your required lengths as one offs or multiple cut pieces. Centreless ground tool steel bar can be supplied, providing a quality precision ground bar to tight tolerances.

Applications

Tool steel 40CrMnMoS8-6 is ideally suited for the production of moulds where improved machinability is required. Typical applications include bolsters and injection moulds, die holders and zinc die casting dies. 40CrMnMoS8-6 is a versatile plastic mould tool steel with high tensile characteristics suitable for many other applications such as shafts and wear strips.

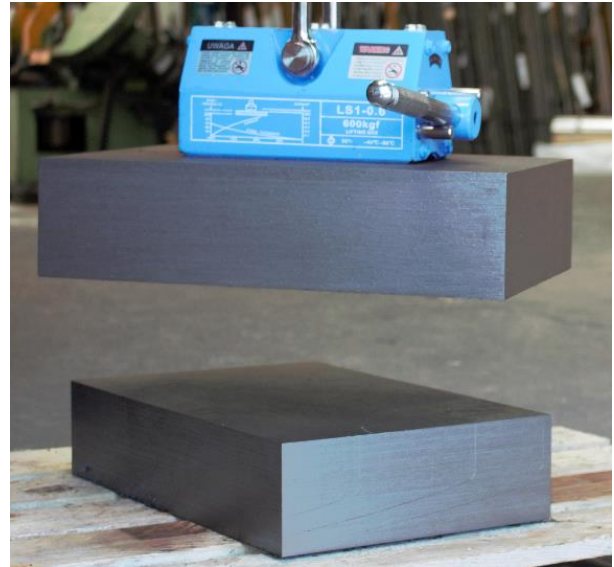

Ground tool steel bar can be supplied, providing a quality precision finish bar to close tolerances.

Contact our experienced sales team who will assist you with your enquiry.

- Flat
- Plate
- Diameter

DIN Standard steel grades we supply

[45NiCrMo16](#) | [55NiCrMoV7](#) | [90MnCrV8](#)
[42CrMo4](#) | [X45NiCrMo4](#) | [60WCrV8](#) | [31CrMoV9](#)
[X100CrMoV5](#) | [X153CrMoV12](#) | [X210Cr12](#)
[60WCrV7](#) | [X210CrW12](#) | [X40Cr14](#) | [X40CrMoV5-1](#)
[40CrMnMoS8-6](#) | [HS6-5-2C](#) | [40CrMnMo7](#)
[X155CrMoV12-1](#) | [100MnCrW4](#)

Typical Analysis

Carbon	0.35-0.45%	Silicon	0.30-0.50%
Manganese	1.40-1.60%	Molybdenum	0.15-0.25%
Chromium	1.80-2.00%	Sulphur	0.05%-0.10%
Phosphorous	0.03% max		

Forging

Heat the 40CrMnMoS8-6 component slowly, allow sufficient time for the steel to become heated through. Begin to forge at 1050°C. Do not forge below 930°C reheating if necessary. After forging, cool very slowly.

Annealing

Heat uniformly to 710-740°C. Soak well, cool slowly in the furnace.

Stress Relieving

When dies made from 40CrMnMoS8-6 are heavily machined, we recommend stabilising the steel just before finish machining in order to relieve machining strains. Heat up to 460-500°C, soak well and cool in air.

Hardening

Heat uniformly to 830-870°C until heated through. Quench in oil.

Tempering

When tempering 40CrMnMoS8-6 heat the steel uniformly, soaking at the tempering temperature for at least one hour per 25mm of section. Allow to cool in still air.

Temperature °C	100	200	300	400	500	600
Hardness HRC	51	50	48	46	42	36
Tensile N/mm ²	1730	1670	1570	1480	1330	1140

Nitriding

Tools machined from 40CrMnMoS8-6 pre-hardened can be nitrided to give a wear resistant surface case of approximately 60 Rockwell C hardness with a case depth of .35mm to 0.5mm. Nitriding also increases the corrosion resistance of 40CrMnMoS8-6. After nitriding at 525°C in ammonia gas the surface hardness of the tool will be approximately 650HV.

Temperature	Time	Approx. Depth of Case
525°C	20 hours	0.30mm
525°C	40 hours	0.35mm
525°C	60 hours	0.50mm

Case Hardening / Carburising

Tools produced from tool steel 40CrMnMoS8-6 may be case hardened, which can achieve a surface hardness of between 55 to 59 Rockwell C.

Tufftriding

At 570°C tufftriding of P20 tool steel will give a surface hardness of approximately 700HV. Allowing two hours treatment the surface hard layer will be approximately 0.1mm.

Flame / Induction Hardening

Induction or flame hardening of will achieve a hardness of 50 to 55HRC. It is preferable to air cool, though smaller components may require forced cooling. Temper immediately after hardening.

Heat Treatment

Heat treatment temperatures, including rate of heating, cooling and soaking times will vary due to factors such as the shape and size of each steel component. Other considerations during the heat treatment process include the type of furnace, quenching medium and work piece transfer facilities. Please consult your heat treatment provider for full guidance on heat treatment of tool steel grades

Quality Assured Supply

40CrMnMoS8-6 tool steel is supplied in accordance with our ISO 9001:2015 registration.



West Yorkshire Steel Ltd
Sandbeck Industrial Estate,
Wetherby, Leeds,
LS22 7DN UK

Call: 01937 584440
Fax: 01937 580128
Email: sales@westyorkssteel.com



QUOTE ME



Information provided on our datasheets has been drawn from various recognised sources, including British, European and International Standards, recognised industry references (printed & online) and manufacturers' data. No guarantee is given that the information is from the latest issue of those sources or about the accuracy of those sources. Material supplied by the Company may vary significantly from this data but will conform to all relevant and applicable standards. Any of the products detailed may be used for a large range of purposes and as WYS has no control over their use; WYS specifically excludes all conditions or warranties expressed or implied by statute or otherwise as to dimensions, properties and/or fitness for any particular purpose, whether expressed or implied. © West Yorkshire Steel Ltd. All Rights Reserved.